

Application of PbWO_4 crystal scintillators in experiment to search for 2β decay of ^{116}Cd

F.A. Danevich ^{a,1}, A.Sh. Georgadze ^a, V.V. Kobychiev ^a,
B.N. Kropivnyansky ^a, S.S. Nagorny ^a, A.S. Nikolaiko ^a,
D.V. Poda ^a, V.I. Tretyak ^a, S.S. Yurchenko ^a

^a*Institute for Nuclear Research, MSP 03680 Kiev, Ukraine*

B.V. Grinyov ^b, L.L. Nagornaya ^b, E.N. Pirogov ^b,
V.D. Ryzhikov ^b

^b*Institute for Scintillation Materials, 61001 Kharkov, Ukraine*

V.B. Brudanin ^c

^c*Joint Institute for Nuclear Research, 141980 Dubna, Russia*

M. Fedorov ^d, M. Korzhik ^d, A. Lobko ^d, O. Miussevitch ^d

^d*Research Institute of Nuclear Problems, 220050 Minsk, Belarus*

I.M. Solsky ^e

^e*Institute for Materials, 79031 Lviv, Ukraine*

Abstract

PbWO₄ crystal scintillators are discussed as an active shield and light-guides in ¹¹⁶Cd double beta decay experiment with CdWO₄ scintillators. Scintillation properties and radioactive contamination of PbWO₄ scintillators were investigated. Energy resolution of CdWO₄ detector, coupled to PbWO₄ crystal as a light-guide, was tested. Efficiency of PbWO₄-based active shield to suppress background from the internal contamination of PbWO₄ crystals was calculated. Using of lead tungstate crystal scintillators as high efficiency 4 π active shield could allow to build sensitive 2 β experiment with ¹¹⁶CdWO₄ crystal scintillators.

Key words: Scintillation detector, PbWO₄ and CdWO₄ crystals, Double beta decay, Low counting experiments

PACS: 29.40.Mc, 23.60.+e, 23.40.-s

1 Introduction

Since 1988 the studies of the ¹¹⁶Cd 2 β decay have been performed in the Solotvina Underground Laboratory [1] with the help of cadmium tungstate crystal scintillators (CdWO₄) enriched in ¹¹⁶Cd to 83%. The results obtained in the different phases of these researches have been published earlier [2]. Beginning from 1998, the experiment was carried out in collaboration with the group from the University and INFN Firenze [3,4,5].

In the apparatus, which is described in detail in [3,5], four ¹¹⁶CdWO₄ crystals (total mass 330 g) were exploited. They are viewed by a low background

¹ Corresponding author. Address: Institute for Nuclear Research, Prospect Nauki 47, MSP 03680 Kiev, Ukraine; tel: +380-44-265-1111; fax: +380-44-265-4463; email address: danevich@kinr.kiev.ua

5" phototube (PMT) through light-guide $\varnothing 10 \times 55$ cm, which is glued of two parts: quartz (25 cm) and plastic scintillator. The enriched $^{116}\text{CdWO}_4$ crystals were surrounded by an active shield made of 15 natural CdWO_4 crystals of large volume with total mass of 20.6 kg. These are viewed by a PMT through an active plastic light-guide $\varnothing 17 \times 49$ cm. The whole CdWO_4 array is situated within an additional active shield made of plastic scintillator $40 \times 40 \times 95$ cm, thus, together with both active light-guides, a complete 4π active shield of the $^{116}\text{CdWO}_4$ detector was provided. Due to the active and passive shields, and as a result of the time-amplitude and pulse-shape analysis of the data, the background rate of $^{116}\text{CdWO}_4$ detectors in the energy region $2.5 - 3.2$ MeV ($Q_{2\beta}$ energy of ^{116}Cd is 2805 keV) was reduced to 0.04 counts/(yr kg keV). It is one of the lowest background which has ever been reached with crystal scintillators. After 14183 h of data taking in the Solotvina Underground Laboratory the half-life limit on $0\nu 2\beta$ decay of ^{116}Cd was set as $T_{1/2} \geq 1.7 \times 10^{23}$ yr at 90% C.L., which corresponds to an upper bound on the effective Majorana neutrino mass $\langle m_\nu \rangle \leq 1.7$ eV [5]. This result is among the strongest world-wide restrictions (in addition to bounds obtained in experiments with ^{76}Ge [6], ^{82}Se and ^{100}Mo [7], ^{130}Te [8], and ^{136}Xe [9]). CdWO_4 crystals possess several unique properties required for a 2β decay experiment: good scintillation characteristics, low level of intrinsic radioactivity, and possibility of pulse-shape discrimination to reduce the background.

To enhance sensitivity of ^{116}Cd experiment to the level of neutrino mass $0.1 - 0.05$ eV, one has to increase the measurement time and the mass of enriched $^{116}\text{CdWO}_4$, improve the energy resolution and reduce the background of the detector. As it was shown by Monte Carlo calculations, the required sensitivity could be achieved by using 150 kg of $^{116}\text{CdWO}_4$ crystals placed into a large

volume of high purity liquid (CAMEO project [10]). The project calls for the background reduction from the current 0.04 counts/(yr keV kg) to $10^{-3} - 10^{-4}$ counts/(yr keV kg). To decrease background, the CAMEO project intends to use ≈ 1000 t of high purity water or liquid scintillator ($\approx 10^{-15}$ g/g for ^{238}U and ^{232}Th) as a shield for $^{116}\text{CdWO}_4$ crystals. Due to low density of these liquids, the necessary dimensions of the shields are huge ($\approx \varnothing 12 \times 12$ m).

We propose an alternative solution for a sensitive 2β decay experiment with $^{116}\text{CdWO}_4$ by using of lead tungstate crystal scintillators as high efficiency 4π active shield. Lead tungstate (PbWO_4) crystal scintillators have been developed as heavy and fast detectors [11] for high-energy physics experiments. Scintillation characteristics of PbWO_4 have been intensively studied during the last decade [12,13,14,15,16]. High registration efficiency to γ quanta, very good transparency in the region of CdWO_4 emission spectrum at the level of a few meters [17], substantial difference of scintillation decay time in comparison with CdWO_4 , well developed tons-scale production [18] make this material very attractive to build a relatively small yet sensitive experiment to search for 2β decay of ^{116}Cd . In this paper we study the possibility of applying PbWO_4 crystals as material for light-guides and active shield in a ^{116}Cd double beta decay experiment with CdWO_4 scintillators.

2 Measurements and results

2.1 Scintillation properties

The main properties of PbWO_4 crystal scintillators are presented in Table 1 where characteristics of cadmium tungstate (CdWO_4) are also given for com-

Table 1

Properties of PbWO_4 and CdWO_4 crystal scintillators.

	PbWO_4	CdWO_4
Density (g/cm^3)	8.28	8.0
Melting point ($^\circ\text{C}$)	1123	1325
Structural type	Sheelite	Wolframite
Cleavage plane	Weak (101)	Marked (010)
Hardness (Mohs)	3	4 – 4.5
Wavelength of emission maximum (nm)	420 – 440	480
Refractive index	2.2	2.2 – 2.3
Effective average decay time* (μs)	0.01	13
Relative photoelectron yield*	6%	100%

*For γ rays, at indoor temperature.

parison. Measurements were carried out with two clear, colorless, undoped PbWO_4 crystals grown by Czochralski method. One crystal ($45 \times 22 \times 22$ mm, 182 g of mass, named PWO-1) was produced in the Institute for Scintillation Materials (Kharkov, Ukraine), and the second one ($32 \times 32 \times 10$ mm, 83 g of mass, PWO-2), produced in the Bogoroditsk Technical Chemical Plant (Russia), was supplied by the Research Institute of Nuclear Problems (Minsk) [18].

Response of the PWO-1 scintillator to γ rays was measured with ^{137}Cs and ^{207}Bi γ sources at temperatures $+24^\circ\text{C}$ and -18°C . The crystal was wrapped

by PTFE reflector tape and optically coupled by Dow Corning Q2-3067 couplant to PMT XP2412. The measured energy spectra are presented in Fig. 1. The energy resolution FWHM=45% and 36% was obtained at the temperature -18°C for 570 keV and 662 keV γ rays, respectively. The relative pulse amplitude has been increased in ≈ 3 times with the detector cooling from $+24^{\circ}\text{C}$ to -18°C .

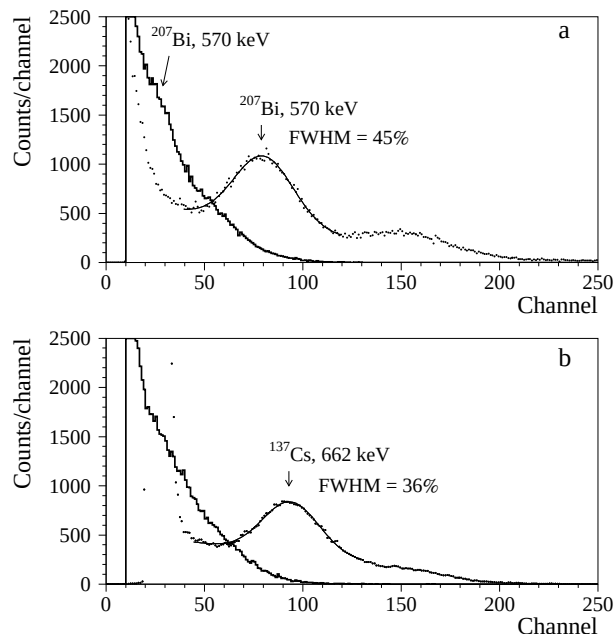


Fig. 1. Energy spectra measured by PbWO_4 scintillation crystal ($45 \times 22 \times 22$ mm) with (a) ^{207}Bi and (b) ^{137}Cs γ sources at two temperatures: $+24^{\circ}\text{C}$ (solid lines) and -18°C (points).

2.2 α/β ratio

The α/β ratio was measured with the PWO-1 crystal using a collimated ^{241}Am α source and thin (≈ 0.65 mg/cm²) mylar absorbers to obtain α particles in the energy range 2.1 – 4.6 MeV. The energies of α particles were determined with the help of a surface-barrier detector. In addition, α peak of ^{210}Po ($E_{\alpha} = 5.30$ MeV) from internal contamination of PbWO_4 crystal by ^{210}Pb (see subsection

2.3) was used. The dependence of the α/β ratio on energy is depicted in Fig. 2 where the α spectrum measured with the ^{241}Am alpha source is shown too. The α/β ratio increases above 3 MeV: $\alpha/\beta = 0.08(2) + 0.025(5)E_\alpha$, while it decreases as $\alpha/\beta = 0.23(4) - 0.024(14)E_\alpha$ at lower energies, where E_α is in MeV. The same behaviour of the α/β ratio was observed for CdWO_4 [4], calcium tungstate (CaWO_4) [19], and zinc tungstate (ZnWO_4) [20] crystal scintillators. The energy resolution for ^{210}Po α peak was measured as 39%, which is comparable with the energy resolution obtained with γ sources.

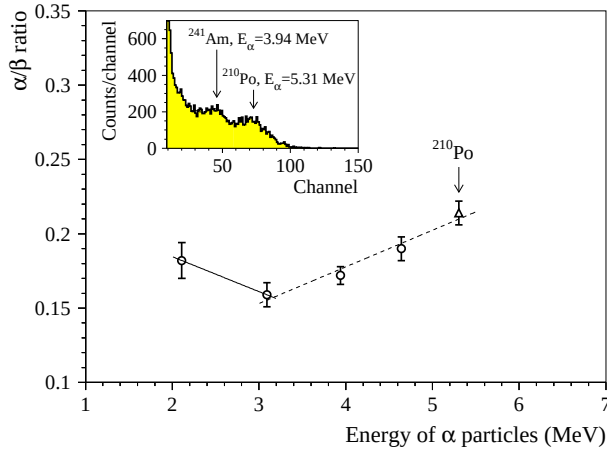


Fig. 2. Dependence of the α/β ratio on energy measured with the PbWO_4 scintillator $45 \times 22 \times 22$ mm. The crystal was irradiated by α particles from ^{241}Am source through absorbers to obtain energies in 2.1 – 4.6 MeV range (circles). Triangle corresponds to α particles of ^{210}Po . (Inset) The α spectrum of ^{241}Am source measured with mylar absorber to obtain energy 3.94 MeV. Second peak at ≈ 73 channel is caused by α decay of ^{210}Po (daughter of ^{210}Pb) inside the scintillator.

2.3 Radioactive contamination of PbWO_4 crystal scintillators

To estimate radioactive contamination, the PWO-1 crystal was measured in the Solotvina Underground Laboratory built in a salt mine 430 m underground ($\simeq 1000$ m of water equivalent) [1]. The crystal was wrapped by PTFE tape

and optically coupled to low radioactive PMT FEU-110. The detector was cooled to -18°C in a temperature-controlled chamber. The shaping time of the spectroscopy amplifier was set to $0.8\ \mu\text{s}$. Amplitude (energy) and arrival time of signals have been recorded by the event-by-event data acquisition system. The energy scale was calibrated with ^{207}Bi γ source. The energy spectrum accumulated during 2.15 h is shown in Fig. 3. The intense peak at the energy $\approx 1.2\ \text{MeV}$ (in γ scale) can be attributed to intrinsic ^{210}Po (daughter of ^{210}Pb from the ^{238}U family) with activity of 53(1) Bq/kg. The major part of events up to the energy $\approx 1\ \text{MeV}$ can be ascribed to β active ^{210}Bi (daughter of ^{210}Pb). The ^{210}Pb contamination of the PWO-2 crystal was measured as 79(3) Bq/kg.

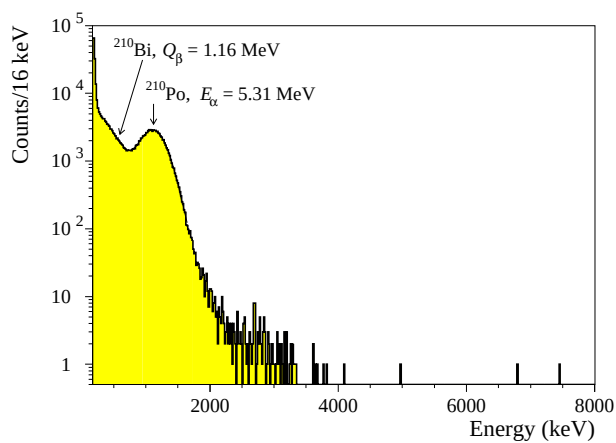


Fig. 3. Energy spectrum of PbWO_4 scintillation crystal measured in the Solotvina Underground Laboratory at the temperature -18°C during 2.15 h. Peak at the energy $\approx 1.2\ \text{MeV}$ (in γ scale) can be attributed to α decay of ^{210}Po from internal contamination of the crystal by ^{210}Pb . Broad distribution up to $\approx 1\ \text{MeV}$ corresponds to β spectrum of ^{210}Bi ($E_{\beta}=1.16\ \text{MeV}$).

Besides, the raw background data accumulated with the PWO-1 were analyzed by the time-amplitude method (described in detail in [21]), when the energy and arrival time of each event were used for find the fast sequence of β and α decays: ^{214}Bi ($Q_{\beta} = 3.27\ \text{MeV}$) $\rightarrow$ ^{214}Po ($E_{\alpha} = 7.69\ \text{MeV}$, $T_{1/2} = 164\ \mu\text{s}$)

$\rightarrow {}^{210}\text{Pb}$ (${}^{238}\text{U}$ family). To select the β decays of ${}^{214}\text{Bi}$, the energy threshold was set at 0.3 MeV (interval from 0.3 MeV to the end of the ${}^{214}\text{Bi}$ β spectrum contains 76% of the ${}^{214}\text{Bi}$ β events). For the α decay of ${}^{214}\text{Po}$, the energy window 1.6–2.6 MeV (94% of α events) and time interval of 90–1000 μs (67% of ${}^{214}\text{Po}$ decays) were chosen. There are no peculiarities in the obtained spectra which could be attributed to the sequence of decays searched for. The limit on the activity of ${}^{226}\text{Ra}$ in the PbWO_4 crystal ≤ 10 mBq/kg was set. Comparing this value with the ${}^{210}\text{Po}$ activity, we can conclude that equilibrium of the uranium chain in the crystal is strongly broken.

Because of shaping time of the spectroscopy amplifier (0.8 μs) exceeds the half-life of ${}^{212}\text{Po}$, and taking into account the α/β ratio, events from the fast sequence of ${}^{212}\text{Bi}$ β decay ($Q_\beta = 2.25$ MeV) and ${}^{212}\text{Po}$ α decay ($E_\alpha = 8.78$ MeV, $T_{1/2} = 0.3$ μs) can result in one event registered in the detector with energy from 2.5 to 5 MeV. In the energy region 3.4–5 MeV (where $\approx 60\%$ of events from the sequence are expected), there are 7 events, which gives the limit on the activity of ${}^{228}\text{Th}$ (${}^{232}\text{Th}$ family) in the PWO-1 crystal ≤ 13 mBq/kg.

The summary of the measured radioactive contamination of the PbWO_4 crystal scintillators (or limits on their activities) is given in Table 2 in comparison with the CdWO_4 detectors.

2.4 PbWO_4 crystal as light-guide for CdWO_4 scintillator

A possibility to use PbWO_4 crystal as a light-guide for CdWO_4 scintillation detector has been tested in measurements. With this aim, the energy resolu-

Table 2

Radioactive contaminations in PbWO_4 and CdWO_4 crystal scintillators.

Chain	Source	Activity (mBq/kg)	
		PbWO_4	CdWO_4 [22,23,24,5]
^{232}Th	^{228}Th	≤ 13	$\leq 0.004 - 0.039(2)$
^{238}U	^{226}Ra	≤ 10	≤ 0.004
	^{210}Pb	$(53 - 79) \times 10^3$	≤ 0.4

tion and relative pulse amplitude were measured with a CdWO_4 crystal in two conditions. First, the CdWO_4 crystal ($10 \times 10 \times 10$ mm, produced in the Institute for Scintillation Materials, Kharkov), wrapped by PTFE reflector tape, was optically coupled to PMT XP2412. The shaping time of the spectroscopy amplifier was set to $16 \mu\text{s}$. The energy resolution was measured with ^{137}Cs , ^{207}Bi , and ^{232}Th γ sources. In particular, the energy resolution FWHM=3.7% was obtained for 2615 keV γ line (Fig. 4 (a)). It should be noted that such an energy resolution was newer reported for CdWO_4 scintillation detector. Then, the CdWO_4 crystal was viewed by the PMT through lead tungstate crystal PWO-1 (wrapped by mylar). The crystals and the PMT were optically coupled by Dow Corning Q2-3067 couplant. The energy resolution of 4.1% (for 2615 keV γ line of ^{232}Th) and 86% of relative pulse amplitude were obtained (see Fig. 4 (b)).

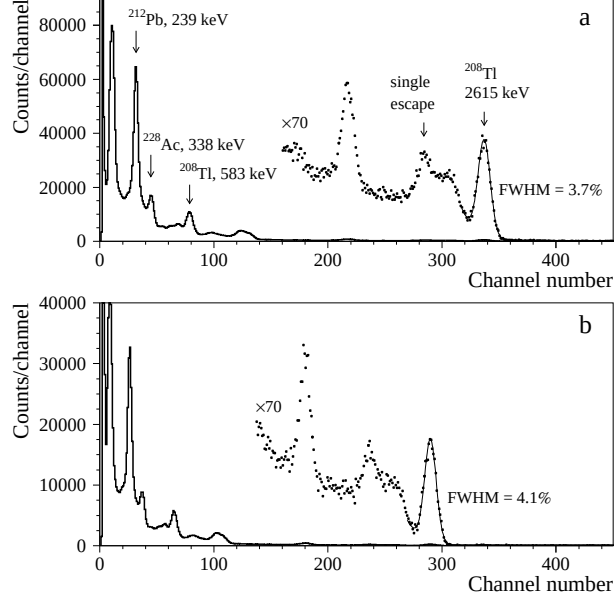


Fig. 4. Energy spectra measured by CdWO_4 scintillation crystal ($10 \times 10 \times 10$ mm) with ^{232}Th γ source in two detector arrangements: (a) the crystal wrapped by PTFE reflector tape optically coupled to PMT; (b) the CdWO_4 crystal viewed by the PMT through the PbWO_4 crystal $45 \times 22 \times 22$ mm as light-guide.

3 Background simulation

The different sources of background in the 2β experiment with $^{116}\text{CdWO}_4$ crystal scintillators were considered in [10]. Here we focus our attention on radioactive contamination of PbWO_4 crystals by ^{232}Th and ^{238}U . Processes with β , α particles and γ rays were simulated with the help of the GEANT4 package [25] and the event generator DECAY0 [26]. The following conditions were taken for the calculations: the CdWO_4 crystal ($\varnothing 5 \times 5$ cm) with the energy resolution (FWHM) 4% at 2.8 MeV is placed in the center of PbWO_4 scintillation detector ($\varnothing 25 \times 25$ cm), contaminated by ^{232}Th and ^{238}U at the level of 10^{-12} g/g. 7.61×10^6 decays of ^{208}Tl inside the PbWO_4 detector were simulated. It corresponds to exposure of ≈ 220 kg $\times$ yr with the CdWO_4 detector. The calculated energy spectrum of the CdWO_4 detector, if no coincidence

would be taken into account, is shown in Fig. 5 (a). The anticoincidence energy spectrum (the energy threshold of PbWO_4 detector was taken to be equal 0.5 MeV) is presented in Fig. 5 (b). There are only two events in the energy interval of $0\nu 2\beta$ peak of ^{116}Cd (2.7–2.9 MeV), which corresponds to the background counting rate 5×10^{-5} counts/(yr keV kg) from the ^{232}Th contamination in PbWO_4 .

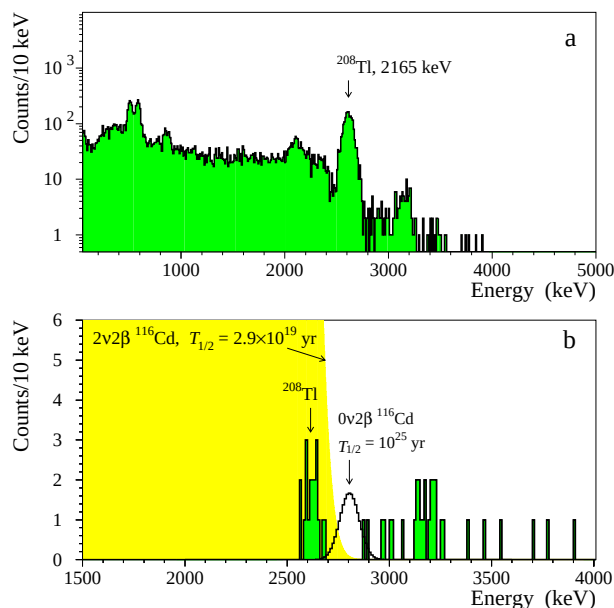


Fig. 5. Monte Carlo simulated (a) response function of $^{116}\text{CdWO}_4$ detector (220 kg $\times$ yr of exposure) to decays of ^{208}Tl inside shielding PbWO_4 crystals (see text). (b) The same as (a) but in anticoincidence with the PbWO_4 detector. Also the $0\nu 2\beta$ peak of ^{116}Cd with $T_{1/2} = 10^{25}$ yr, and two neutrino 2β distribution ($T_{1/2} = 2.9 \times 10^{19}$ yr) are shown.

The contamination of PbWO_4 crystals by ^{226}Ra is even less dangerous. The Monte Carlo calculations show that no events above the energy of 2 MeV will be registered in the CdWO_4 detector during ≈ 220 kg $\times$ yr of exposure.

4 Discussion

The response functions of a detector with enriched $^{116}\text{CdWO}_4$ crystals (≈ 220 kg $\times$ yr of exposure) for two neutrino ($T_{1/2} = 2.9 \times 10^{19}$ yr [5]) and neutrinoless 2β decay of ^{116}Cd with half-life 10^{25} yr are presented in Fig. 5 (b). Sensitivity of the experiment to neutrinoless 2β decay of ^{116}Cd is at the level of $\lim T_{1/2} = 10^{26}$ yr (which corresponds to the limit on neutrino mass of ≈ 0.07 eV [27]). It is evident that the $0\nu 2\beta$ decay with $T_{1/2} \approx 10^{25}$ yr (neutrino mass ≈ 0.2 eV) would be certainly observed at this level of sensitivity.

The size of PbWO_4 active shield² in a set-up could be approximately of $50 \times 50 \times 50$ cm. 32 enriched $^{116}\text{CdWO}_4$ crystals $\oslash 5 \times 5$ cm are viewed by 3" PMT through logarithmic-spiral PbWO_4 crystals. PbWO_4 as light-guide has an advantage in comparison with plastic or quartz. Because of high index of refraction (2.2), logarithmic-spiral type light-guide can be made of less than 60 mm in diameter, that allows to use 3" PMT (which typically have lower mass, better energy resolution and lower level of noise) instead of 5" PMT in the Solotvina experiment [5]. Assuming ≈ 50 cm of passive lead shield and ≈ 50 cm polyethylene antineutron shield, dimensions of the set-up are much more compact ($2.5 \times 2.5 \times 2.6$ m) if to compare with "water shield" apparatus ($\approx \oslash 12 \times 12$ m) proposed in [10].

To get such an impressive result, the problem of low-radioactive PbWO_4 crystals production should be solved. In particular, content of ^{210}Pb should be decreased: high counting rate (and, thus, big number of random coincidences)

² It should be stressed that CdWO_4 crystals, successfully used in the Solotvina experiment [5], can be also used as active shield detector.

in ^{210}Pb – ^{210}Bi – ^{210}Po decays, observed in the current measurements, creates a problem for performing the time-amplitude analysis of events to search for the specific decay chains. It is well known that the freshly smelted lead is contaminated by ^{210}Pb at the level of hundreds Bq/kg, while its contamination by uranium and thorium is substantially less [28]. As the first step, we are going to grow PbWO_4 crystals from archaeological lead aiming to obtain PbWO_4 crystals less contaminated by ^{210}Pb ³. As the next step, we foresee to estimate radioactive contamination of PbWO_4 crystals in low-background measurements by using the time-amplitude and pulse-shape (to select fast sequence of β and α decays from the ^{212}Bi – ^{212}Po chain) analyses. As it was demonstrated in the experiments with CdWO_4 scintillators, the sensitivities are at the level of a few $\mu\text{Bq/kg}$ for ^{228}Th , ^{226}Ra , and ^{227}Ac [5].

The energy threshold of the shielding PbWO_4 detector of 0.5 MeV can be achieved even with undoped scintillators at room temperature (see Fig. 1). However, as it was shown in [13], dopants like molybdenum and terbium can improve light yield of this scintillator, which allow to decrease the energy threshold of PbWO_4 -based active shield.

5 Conclusions

Scintillation properties of PbWO_4 crystal scintillators were studied. The energy resolution FWHM=36% was measured for the 662 keV γ line of ^{137}Cs at -18°C . The α/β ratio was measured in the energy interval 2–5.3 MeV. The dependence of the α/β ratio on energy of α particles was observed. Radioac-

³ For instance, only limit ≤ 4 mBq/kg on ^{210}Pb contamination in lead tungstate crystal produced from Roman lead was reported in [29].

tive contamination of two PbWO_4 crystals was measured in the Solotvina Underground Laboratory. Both crystals are considerably polluted by ^{210}Po at the level of $50 - 80$ Bq/kg. For ^{228}Th (^{232}Th family) and ^{226}Ra (^{238}U) activities only limits were set at the level of 13 and 10 mBq/kg, respectively.

The excellent energy resolution of $\text{FWHM}=3.7\%$ was obtained for 2615 keV γ line with high quality CdWO_4 crystal scintillator $10 \times 10 \times 10$ mm. The energy resolution of 4.1% (2615 keV γ line of ^{232}Th) and 86% of relative pulse amplitude was obtained for CdWO_4 scintillator viewed through PbWO_4 crystal as light-guide. We expect an improvement of the light collection and the energy resolution of CdWO_4 detector by using the logarithmic-spiral PbWO_4 light-guide.

Monte Carlo simulation and measurements demonstrate good abilities of PbWO_4 crystals to build 4π active shield for a sensitive ^{116}Cd double beta decay experiment with CdWO_4 scintillators.

6 ACKNOWLEDGEMENT

The authors would like to thank Prof. P.G. Bizzeti and Prof. P. Maurenzig from the Dipartimento di Fisica, Università di Firenze and INFN (Firenze, Italy) for careful reading of the manuscript and useful comments and discussion.

References

- [1] Yu.G. Zdesenko et al., Proc. 2nd Int. Symp. Underground Physics, Baksan Valley, USSR, August 17–19, 1987 – Moscow, Nauka, 1988, p. 291.
- [2] F.A. Danevich et al., Pis'ma Zh. Eksp. Teor. Fiz. 49 (1989) 417 [JETP Lett. 49 (1989) 476];
Yu.G. Zdesenko, J. Phys. G: Nucl. Part. Phys. 17 (1991) s243;
F.A. Danevich et al., Proc. 3-rd Int. Symp. on Weak and Electromagnetic Inter. in Nuclei (WEIN-92), Dubna, Russia, 1992 – World Sci. Publ. Co., 1993, p. 575;
F.A. Danevich et al., Phys. Lett. B 344 (1995) 72;
A.Sh. Georgadze et al., Phys. At. Nucl. 58 (1995) 1093;
F.A. Danevich et al., Nucl. Phys. B (Proc. Suppl.) 48 (1996) 232;
F.A. Danevich et al., Nucl. Phys. A 643 (1998) 317;
F.A. Danevich et al., Nucl. Phys. B (Proc. Suppl.) 70 (1999) 246.
- [3] F.A. Danevich et al., Phys. Rev. C 62 (2000) 045501;
P.G. Bizzeti et al., Nucl. Phys. B (Proc. Suppl.) 110 (2002) 389;
F.A. Danevich et al., Nucl. Phys. A 717 (2003) 129.
- [4] F.A. Danevich et al., Phys. Rev. C 67 (2003) 014310.
- [5] F.A. Danevich et al., Phys. Rev. C 68 (2003) 035501.
- [6] H.V. Klapdor-Kleingrothaus et al., Eur. Phys. J. A 12 (2001) 147;
C.E. Aalseth et al., Phys. Rev. C 59 (1999) 2108; Phys. Rev. D 65 (2002) 092007.
- [7] R. Arnold et al., Pis'ma Zh. Eksp. Teor. Fiz. 80 (2004) 429.
- [8] C. Arnaboldi et al., Phys. Lett. B 557 (2003) 167; 584 (2004) 260.
- [9] R. Luescher et al., Phys. Lett. B 434 (1998) 407;
R. Bernabei et al., Phys. Lett. B 546 (2002) 23.

- [10] G. Bellini et al., Phys. Lett. B 493 (2000) 216; Eur. Phys. J. C 19 (2001) 43.
- [11] V.G. Barishevsky et al., Nucl. Instr. and Meth. A 322 (1992) 231.
- [12] M. Kobayashi et al., Nucl. Instr. Meth. A 399 (1997) 261.
- [13] A. Annenkov et al., Nucl. Instr. Meth. A 450 (2000) 71.
- [14] M. Kobayashi et al., Nucl. Instr. Meth. A 465 (2001) 428.
- [15] M. Kobayashi et al., Nucl. Instr. Meth. A 484 (2002) 140.
- [16] A. Borisevich et al., Nucl. Instr. Meth. A, in press.
- [17] S. Baccaro et al., Nucl. Instrum. Meth. A 385 (1997) 209.
- [18] A. Annenkov et al., Nucl. Instr. Meth. A, in press.
- [19] Yu.G. Zdesenko et al., Nucl. Instr. Meth. A, in press.
- [20] F.A. Danevich et al., nucl-ex/0409014, submitted to Nucl. Instr. Meth. A.
- [21] F.A. Danevich et al., Nucl. Phys. A 694 (2001) 375.
- [22] A.Sh. Georgadze et al., Instr. Exp. Technique 39 (1996) 191.
- [23] S.Ph. Burachas et al., Nucl. Instr. Meth. A 369 (1996) 164.
- [24] F.A. Danevich et al., Z. Phys. A 355 (1996) 433.
- [25] S. Agostinelli et al. (GEANT4 Collaboration). Nucl. Instr. Meth. A 506 (2003) 250; <http://geant4.web.cern.ch/geant4/>.
- [26] O.A. Ponkratenko et al., Yad. Fiz. 63 (2000) 1355 [Phys. Atom. Nucl. 63 (2000) 1282].
- [27] A. Staudt et al., Europhys. Lett. 13 (1990) 31.
- [28] R.L. Brodzinski et al., Nucl. Instr. Meth. A 239 (1985) 207.
- [29] A. Alessandrello et al., Nucl. Instr. Meth. A 409 (1998) 451.